

35 hasil tes turnitin pigment influence

by Dumasari Dumasari

Submission date: 11-Jul-2020 04:23PM (UTC+0700)

Submission ID: 1356087058

File name: 35.pdf (281.38K)

Word count: 5578

Character count: 27856

Influence of surface roughness of ten tropical woods species on their surface free energy, varnishes wettability and bonding quality

Wayan Darmawan and Monica Br. Ginting
Department of Forest Products, Faculty of Forestry, Bogor Agricultural University, Bogor Indonesia

Asih Gayatri
Department of Chemistry, University of Indonesia, Jakarta Indonesia

Rumanintya L. Putri
Department of Economic, Balitar Islamic University, Blitar, Indonesia

Dumasari Lumongga
Department of Agriculture, Muhammadiyah University of Purwokerto, Purwokerto, Indonesia, and

Aulia Hasanusi
Department of Research and Development, Perhutani Research Institution, Cepu Indonesia

Abstract

Purpose – The surface characteristics of wood such as surface roughness, surface free energy (SFE) and wettability are important properties influencing further manufacturing processes such as gluing and coating. The purpose of this study is to determine the influence of surface roughness of ten tropical woods on their SFE, wettability and bonding quality for water-based acrylic and solvent-based alkyd varnishes.

Design/methodology/approach – The woods tested in this study were fast-growing teak, afrika, sungkai, mindi, merbau, durian, lamtoro, pulai, acacia and kempas. Wood surfaces were prepared in unsanded and sanded using an abrasive paper of 120 grits. SFE values were calculated based on the Rabel method. Wettability values were measured based on the contact angle between varnish liquids and wood surfaces using the sessile drop method, and the S/G model was used to evaluate the wettability of the varnishes on the woods surface. The bonding quality of the varnishes was measured using a cross-cut test based on the ASTM 3359-02 standard.

Finding – The results show that unsanded kempas wood had the roughest surface with a Ra value of 16.24 μm , whereas sanded lamtoro wood has the smoothest surface with a Ra value of 6.86 μm . The unsanded afrika wood had the highest SFE value of 53.61 mJ/m^2 , whereas sanded fast-growing teak had the lowest SFE value of 36.17 mJ/m^2 . Sanded merbau woods had the lowest K value of 0.022 for the water-based acrylic varnish, whereas unsanded afrika wood had the highest K value of 9.253 for the alkyd varnish. Afrika wood with the highest K values (highest wettability) for both acrylic and alkyd varnishes produced the highest bonding quality (grade 4-5). Compared to the water-based acrylic varnish, the solvent-based alkyd varnish was more wettable and generated better bonding quality.

Research limitations/implications – Improving the quality of fast-growing wood from plantation by painting could be considered to increase their use for higher value wood products.

Practical implications – Compared to water-based acrylic varnish, solvent-based alkyd varnish was more wettable and generated better bonding quality.

Originality/value – The originality of this research is to evaluate the values of surface free energy. SFE could be used to quantitatively determine the wettability of paints liquid in the surface of wood.

Keywords Surface roughness, Wettability, Acrylic and alkyd varnish, Bonding quality, Surface free energy, Tropical wood species

Paper type Research paper

1. Introduction

Demand for wood as a raw material in the level of production continues to sustainably increase, especially in the production of all categories of processed timber such as

sawnwood, plywood and laminated veneer lumber, chipwood, veneer and wood pulp. In many other ways, the use of wood as raw material still cannot be replaced because it is relatively cheap, strong, environmentally friendly and has an attractive appearance with the characteristic that could not be identified in other materials.

The current issue and full text archive of this journal is available on Emerald Insight at: <https://www.emerald.com/insight/0369-9420.htm>

The authors thank the Directorate for Research and Community Service of the Ministry of RISTEK-DIKTI of the Republic of Indonesia for the research grant.



Pigment & Technology
© Emerald Publishing Limited [ISSN 0369-9420]
[DOI: 10.1108/PRT-01-2020-0005]

Received 28 January 2020
Revised 13 February 2020
Accepted 17 March 2020

Ten tropical wood species (fast-growing teak, afrika, sungkai, mindi, merbau, durian, lamtoro, pulai, acacia and kempas) could be extensively used for multiple purposes. These woods might be suitable for construction, furniture, paper, packing materials and panel wood. Merbau and kempas are high-density wood species with high strength (class I-II) (Martawijaya et al., 2005). Durian, sungkai, acacia, afrika, mindi and fast growing teak are medium density wood species with good strength (class II-III) (Martawijaya et al., 2005). Pulai and lamtoro are low-density wood species with low strength (class IV-V) (Martawijaya et al., 2005). Some wood species can be easily machined (Darmawan et al., 2006; Darmawan et al., 2015). There is abundant information about the physical or mechanical properties of these ten tropical woods; however, the information about the surface properties of these woods is still limited and is not investigated yet. The surface properties of wood are one of the most important properties influencing further manufacturing process such as finishing or their adhesive strength characteristics. To complete the information for better utilization of woods, the surface properties of ten woods species need to be studied.

The application of coating such as varnish on wood surfaces is commonly performed. The coating protects wood surface and gives a desired appearance. The coating aims to provide better aesthetic value to wood and serves to cover up some of the weaknesses of wood in terms of both colour and texture. The coating protects wood from external conditions such as weather, temperature, air, sunlight or wood-damaging organisms (Crump, 1993).

According to Moita and Moreira (2003), the increase in surface roughness leads to a decrease in contact angle. Wood with a high surface roughness value has a low contact angle value because the varnish liquid spreads and seeps more quickly into the wood. One of the criteria that can be used to analyze the wetting behaviour of wood is the measurement of its contact angle. Contact angle values larger than 90° indicate a poor wetting characteristics of the varnish liquid which it will be difficult for the varnish liquid to wet a surface (Yuan and Lee, 2013).

Wettability refers to how easily and efficiently a liquid spread over a solid surface (Bal, 2012). The wettability can be characterized by certain parameters such as contact angles, surface free energy (SFE) and adherence (Wälinder, 2002). The amount of SFE and surface tension affect the value of wood wettability (Yuningsih et al., 2019). Both wettability and SFE are important parameters to support information on interactions between wood surface and liquids (such as water, adhesives and wood finishes) (Qin et al., 2014; Wälinder and Gardner, 2002; Gindl et al., 2004; Rathke and Sinn, 2013). Wettability should be one of important indicator for evaluating the bonding between coatings and wood surface. Higher wettability provides better bonding quality of varnish (Darmawan et al., 2018). Wettability can be determined by measuring the contact angle between liquid and surface. Many factors such as surface tension phenomena, viscosity of liquids, wood aging, drying processing and defects influence penetration (Qin et al., 2014). The purpose of this study is to investigate and to evaluate surface characteristics in term of surface roughness and SFE for ten tropical woods species, as well as their wettability and bonding quality for water-based acrylic and solvent-based alkyd varnishes.

2. Experimental

2.1 Sample preparation

Wood samples were prepared from ten species of fast-growing teak (*Tectona grandis*), afrika (*Maesopsis eminii*), sungkai (*Peronema canescens*), mindi (*Melia azedarach*), merbau (*Intsia bijuga*), durian (*Durio zibethinus*), lamtoro (*Leucaena leucocephala*), pulai (*Alstonia scholaris*), acacia (*Acacia mangium*) and kempas (*Koompassia malaccens*). Lumber of the woods were surfaced in a planer. The planed lumbars were cut to produce samples for roughness measurement and wettability test. Wood specimens in dimension of 20 cm x 12 cm x 2 cm (longitudinal x tangential x radial) were prepared by cutting the lumbars. The wood specimens were placed in an air-conditioned room at 23 ± 2°C and relative humidity of 80% ± 5% for two weeks before the roughness and wettability test. The room was lighted and kept clean to retain the surface of wood samples in the same condition. The varnishes used for the wettability test were water-based acrylic and solvent-based alkyd. A mixture of alkyd varnish (90 %) and oil thinner (10 %) was prepared and uniformly stirred. Moreover, another mixture of acrylic varnish (90 %) and water (10 %) was prepared. The viscosity of the alkyd and acrylic mixtures measured by viscometer was in the average of 0.2 and 1.5, respectively.

2.2 Surface roughness test

A set of test specimen was kept unsanded as the control. The other specimen was sanded 50 times parallel to the length with abrasive papers of P120. The measurement of surface roughness of unsanded and sanded wood specimens was perpendicularly performed to the fibre direction at five different positions on tangential surface of each sample using Mitutoyo type SJ-210 tester. The roughness on the tangential surface was measured for decorative purposes. Compared to radial lumber, the tangential lumber provided better decorative appearance, particularly for furniture products coated with clear coats. The roughness measurement according to ISO 4287:1997 (International Standard, 1997) was performed with a diamond tip radius of 5 µm, tracing length of 6 mm, cut off of 0.8 mm and speed of 0.5 mm/s. The value evaluated was the arithmetical mean roughness (Ra).

2.3 Contact angle measurement

The dynamic contact angles of selected standard liquids (water, methanol, toluene and glycerin) for measuring SFE and of acrylic varnish for measuring wettability were performed with a video measuring system using a high-resolution CCD camera. During measurement, wood specimen was placed on the top of a table in front of the CCD video camera. To obtain the same droplets, the drop of selected standard liquids and acrylic varnish with volume of 20 µl were dropped by a syringe using a screw method. The drop shapes on the wood surface were captured by the CCD camera and saved for 180 s. To obtain the contact angle, five droplets per sample were captured for each standard liquid and acrylic varnish. Each of the captured video images was then cut to an individual image at an interval of 10 s for a total duration of 180 s. Image-J 1.46 with drop-snakes plugin analysis was used to measure the contact angle (θ) of the individual image of the drop. The contact angles of each droplet

The surface of wood specimen were measured on both the left side and right side of the droplet, and then the values were averaged. To obtain a curve of contact angle versus wetting time, a total of nineteen data points were then taken for each recorded drop. The contact angle tests were then conducted at a room temperature of $23 \pm 2^\circ\text{C}$ and relative humidity of $80\% \pm 5\%$.

2.4 Determination of equilibrium contact angle and constant contact angle change rate

To determine the equilibrium contact angle (θ_e) value, a segmented regression model was used. It is assumed that developing contact angle during wetting process can be described by two functions in a curve (Figure 1). The first function is a steep slope (quadratic) of the curve over the first second beginning of spreading and penetration, whereas the second function is a constant slope (plateau) for the later part of the curve (constant contact angle). The fitted regression model for the functions takes the form of a quadratic model with a plateau. The transition point between the two functions (t_e) was directly obtained using nonlinear least-squares procedures (PROC NLIN) in SAS STAT (SAS Institute, 2004).

The contact angle change rate depends on the contact angle at a particular time. In this work, the contact angle change rate (K-value) on the S/G model (Shi and Gardner, 2001) was used to quantitatively evaluate the wettability. The equation of S/G model can be expressed as follows:


$$\theta = \frac{\theta_i \cdot \theta_e}{\theta_i + (\theta_e - \theta_i) \exp \left[K \left(\frac{\theta_e}{\theta_e - \theta_i} \right) t \right]} \quad (1)$$

where θ is the contact angle at a certain time, θ_i is the initial contact angle, θ_e is equilibrium contact angle, K is the constant contact angle change rate and t is wetting time. A non-linear regression model was then used to calculate the K value using the defined function to fit the S/G equation using XLSTAT Addinsoft (2007).

2.5 Determination of surface free energy components

Many methods have been used to calculate the SFE of wood. The two-liquid method is modified to be a multi-liquid method to determine the SFE value, and its components are proposed by Rabel (1971) using a regression line as in Equation (2):

Fig. 24. 1 Determination of equilibrium contact angle (θ_e) from a plot of the contact angle as a function of time using a segmented regression model

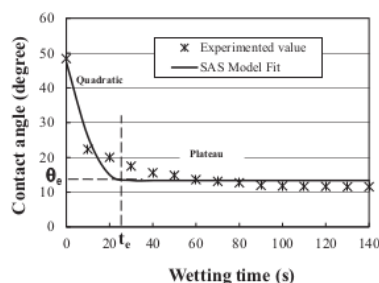

$$(1 + \cos \theta_e) \frac{\gamma_l}{(\gamma_l^d)^{1/2}} = (\gamma_s^d)^{1/2} + (\gamma_s^p)^{1/2} \left(\frac{\gamma_l^p}{\gamma_l^d} \right)^{1/2} \quad (2)$$

where θ_e is equilibrium contact angle, γ_l is the value of total surface tension, γ_l^d is dispersive surface tension, γ_s^d is dispersive component of SFE, γ_s^p is polar component of SFE and γ_l^p is polar surface tension. For determining wood SFE (γ_s), the size of the equilibrium contact angle (θ_e) of the standard liquid droplets (with known γ_l) on the surface of the woods samples is used. In a linear regression line ($Y = A + BX$), as $Y = (1 + \cos \theta_e) \frac{\gamma_l}{(\gamma_l^d)^{1/2}}$, $X = \left(\frac{\gamma_l^p}{\gamma_l^d} \right)^{1/2}$, the slope (B) will be $(\gamma_s^p)^{1/2}$ and the intercept (A) will be $(\gamma_s^d)^{1/2}$. The values of X and Y in this study were calculated by the four standard liquids, shown in Table 1. Furthermore, the Y value was calculated by measuring the contact angles of the standard liquids in Table 1 on each surface of woods specimens. The value of SFE should be $A^2 + B^2 = ((\gamma_s^d)^{1/2})^2 + ((\gamma_s^p)^{1/2})^2$.

2.6 Coating application and bonding test

The unsanded and sanded wood samples were coated by the abovementioned varnish types for bonding quality evaluation. Two coats were then applied on the wood surfaces to achieve a total application of 150 g/m^2 wet film and a dry film thickness of $60 \pm 5 \mu\text{m}$. Based on the surface area of the samples, the required weight of each coat to achieve these spread rates was calculated. The varnishes were then applied by brush on the front face and the back of the samples. A drying time of 24 h was allowed before the second coat was applied. When the second coat had dried, the coated samples were conditioned for 1 week in a clean room at a temperature of approximately 25°C and a relative humidity of 75%.

To evaluate the resistance of the coating films to separation from wood surfaces, a cross-cut tape test method was applied (ASTM, 1997). A cross-cut pattern was made through the film using a sharp cutter head. Pressure-sensitive tape was then applied over the cut. The tape was smoothed into place using pencil eraser over the incision, and then the tape was removed by pulling it off rapidly back over itself close to an angle of 180° . Bonding quality was then assessed on a 0 to 5 scale; note that scale 5 is 0% area removed, whereas scale 0 is greater than 65% area removed. The five cross-cut patterns per sample were

Table 1 The value of total surface tension, polar component of surface tension and dispersive component of surface tension for standard liquids (mJ/m^2)

Liquids	γ^p	γ^d	γ^l
Water	21.8	51.0	72.8
Methanol (50%)	12.9	22.7	35.6
Toluene	2.3	26.1	28.4
Glycerin	30.0	34.0	64.0

es: γ^p , polar component of surface tension; γ^d , dispersive component of surface tension; γ^l , the value of total surface tension

developed for each varnish coating; two samples were used and ten measurements of cross-cut were obtained. The scales of the adhesion were then averaged.

3. Results and discussion

3.1 Surface roughness


In terms of surface quality, surface roughness is an important property, particularly in finishing treatments (Buyuksari et al., 2011). The result in Figure 2 shows that sanding with 120 grit paper contributed to a decrease in surface roughness values (Ra) for all wood species. The result indicates that kempas had the roughest surface for both sanded and unsanded wood, a Ra value of 11.06 and 16.24 μm , respectively. Lamtoro had the smoothest surface after sanding with a Ra value of 6.86 μm . Note that the surface roughness of wood can be affected by certain factors such as annual ring variation, density, cell structure, latewood/earlywood ratio and type of machining (Amorim et al., 2013; Kilic et al., 2005).

A higher surface roughness produces a higher surface hydrophilicity that tends to produce better wetting with a lower contact angle (Piao et al., 2010). The void size in the wood may influence surface roughness. Wood with a larger lumen and diameters would usually result in open grain after machining, which leads to higher surface roughness (Syahirah et al., 2019). In this work, surface roughness of the woods tested should be important for determining its SFE and wettability for both water-based acrylic and oil-based alkyd varnish.

3.2 Surface free energy

To calculate the SFE of the tested woods, the equilibrium contact angle (θ_e) as measured. The equilibrium contact angles were then calculated using a segmented regression model; the results are shown in Table 2. Unsanded frika wood had the lowest θ_e of 20.6° and 25.2° for water-based acrylic and solvent-based alkyd varnishes, whereas sanded lamtoro wood had the lowest θ_e value of 6.1° and 6.8° for water-based acrylic and solvent based alkyd varnishes, respectively. Otherwise, unsanded and sanded merbau woods were the highest in θ_e value of 39.8° and 41.8°, respectively for water-based acrylic varnish, and 14.2° and 15.9°, respectively, for solvent based alkyd varnish. The values of these θ_e

Figure 2 The values of surface roughness for the ten tropical wood species

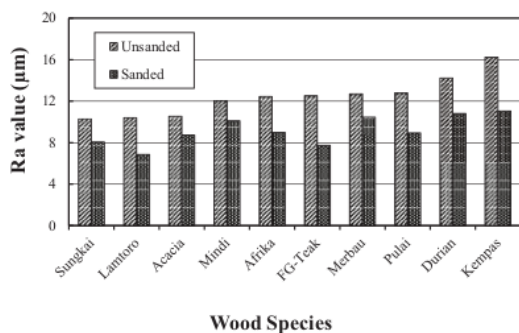

Note: FG-Teak = Fast growing teak

Table 2 The value of equilibrium contact angle for 10 tropical wood species

Wood	Water-based acrylic paint		Oil-based alkyd paint	
	θ_e (Unsanded)	θ_e (Sanded)	θ_e (Unsanded)	θ_e (Sanded)
Afrika	20.6	25.2	6.1	7.1
Acacia	29.0	29.2	8.9	9.8
Kempas	26.9	28.2	9.7	12.7
Lamtoro	29.4	29.7	6.3	6.8
Durian	28.3	30.0	7.3	7.5
Sungkai	29.6	31.7	11.3	12.1
Pulai	31.7	31.8	8.2	10.1
Mindi	30.1	34.3	8.9	10.3
FG-Teak	33.7	37.9	10.8	11.4
Merbau	39.8	41.8	14.2	15.9

Note: FG-Teak = Fast growing teak

demonstrated a correlation with a surface roughness of the woods, in which a rougher wood surface tended to produce a lower θ_e value.

The results in Table 2 show that θ_e values of acrylic and alkyd varnishes for all wood surfaces were prominently different. The water-based acrylic varnish generated higher values of θ_e . Its higher viscosity (1.5 poise) compared to solvent-based alkyd varnish (0.3 poise) could be the reason. The lower θ_e of solvent-based alkyd varnish indicated the ease in spreading the varnish liquid and lead to beneficial substrate wetting and penetration in wood. The lower θ_e of solvent-based alkyd indicates that it should create more intimate contact on wood surface than water-based acrylic.

Table 3 shows the SFE values of woods; the SFE decreased as the roughness of the woods decreased. It was reported by Gindl et al. (2001) that sanded surfaces of woods show lesser total SFEs. Unsanded and sanded fast-growing teak had the lowest SFE values of 38.60 and 36.17 mJ/m^2 , respectively, whereas unsanded afrika and sanded kempas woods were the highest in SFE values of 53.61 and 45.46 mJ/m^2 , respectively. The higher SFE value of the wood imposed the higher energy on the surfaces of the wood that can be used for breakdown the liquid to spread and penetrate on their surfaces. A rougher

Table 3 The value of total SFE and components for ten wood species (in mJ/m^2)

Wood	γ_s^d	Unsanded		Sanded		
		γ_s^p	$>\gamma_s$	γ_s^p	γ_s	
FG-Teak	23.60	15.00	38.60	26.55	9.62	36.17
Merbau	40.29	6.96	47.26	43.35	3.57	46.92
Acacia	41.69	7.31	49.00	36.60	7.16	43.76
Sungkai	42.16	7.64	49.80	35.52	7.85	43.37
Pulai	40.78	9.65	50.43	30.61	12.12	42.72
Durian	35.63	14.91	50.54	32.03	14.12	46.15
Mindi	35.53	15.52	51.05	27.91	17.69	45.60
Lamtoro	34.25	16.87	51.12	22.24	19.11	41.35
Kempas	46.49	6.85	53.34	41.46	7.10	48.55
Afrika	44.48	9.13	53.61	36.02	9.44	45.46

Notes: γ_s^p , polar component of SFE; γ_s^d , dispersive component of SFE; γ_s , the value of total SFE

Surface roughness

Wayan Darmawan et al.

wood surface tended to produce a higher SFE. This could be attributed to the contact area on the rougher surfaces, which was higher than that on smoother surfaces.

3.3 Wettability

For quantifying the wettability of varnish liquid on the surface of wood, K value is important. K-value of 0 indicates very poor wettability. The K values of woods tested in this work are shown in Table 4. Both unsanded and sanded merbau woods demonstrated the lowest K values of 0.027 and 0.022, respectively, for water-based acrylic varnish. The unsanded pulai and sanded sungkai showed the lowest K value of 3.627 and 3.485, respectively, for the solvent-based alkyd varnish. Otherwise, unsanded and sanded afrika woods generated the highest K values of 0.055 and 0.051, respectively, for the acrylic varnish, and of 9.253 and 8.202, respectively, for the alkyd varnish.

Table 4 shows that the solvent-based alkyd showed larger K values compared to water-based acrylic because solvent-based alkyd was lower in viscosity (0.3 poise) compared to water-based acrylic varnish (1.5 poise). According to Gavrilovic-Grmusica et al. (2012), wettability value decreased with increase in the viscosity of an adhesive. A decrease in surface tension within the liquid could result in greater wettability. The solvent-based alkyd varnish had a lower surface tension of 66.32 mJ/m² compared to water-based acrylic varnish of (80.52 mJ/m²). Moreover, it appears from the results in Table 4 that the unsanded wood samples had a larger K value than sanded woods for both acrylic and alkyd varnish. As noted in Darmawan et al. (2018), rougher surface of woods generated lower contact angle and ensures better wettability. Shi and Gardner (2001) reported that with greater K-values, the time required for the liquid to spread and penetrate on the wood surfaces is faster. By considering the fact that both acrylic and alkyd varnishes in this study were prepared and applied based on the manufacturer's instructions, it can be concluded that alkyd varnish produced better wettability compared to acrylic varnish for all ten wood surfaces.

3.4 Bonding quality

Bonding qualities of ten wood species are presented in Table 5. It is seen from Table 5 that, compared to sanded woods, bonding quality of unsanded woods was slightly better. Both

Pigment & Resin Technology

Table 5 Bonding quality of water-based acrylic paint and oil-based alkyd paint for ten wood species

Wood	Water-based acrylic Paint		Oil-based alkyd Paint	
	Unsanded	Sanded	Unsanded	Sanded
Afrika	5	5	5B	4B
Lamtoro	4B	3B	3B	3B
Durian	3B	3B	5B	4B
Acacia	4B	3B	4B	3B
Pulai	3B	3B	3B	3B
Mindi	3B	3B	5B	4B
FG-Teak	5B	4B	5B	4B
Sungkai	5B	4B	5B	5B
Kempas	3B	2B	5B	2B
Merbau	5B	3B	3B	3B

Note: FG-Teak = fast growing teak

afrika and sungkai provided the highest average of bonding quality compared to others because of their high K values. Pulai and lamtoro provided the lowest average of bonding quality because of their low K values.

Anatomical structure would be one of the major factors affecting the interaction between coating and wood material. Afrika wood had a porous structure that would result in better absorption and penetration of coating to its surface, and then cause a higher magnitude of interface that enhanced bonding quality characteristics. The results indicate that sanding decreased the bonding quality value. The increase in surface roughness will tend to increase the bonding quality. It was reported by Darmawan et al. (2018) that when the surface was smoother, the coating lacked mechanical interlocking with the substrate, thus weakening the adhesion. A rough surface was proposed to enhance intrinsic adhesion by providing greater interfacial area. The coating liquid flowed and filled the wood pores, holes, crevices and microvoids to achieve a strong bond between the wood surface and coating material.

The results in Table 5 demonstrate that, for most of ten wood species, alkyd varnish produced a higher bonding quality than acrylic varnish. The better wettability of alkyd varnish (higher K values) contributed to better bonding quality.

Table 4 K-values of water-based acrylic paint and oil-based alkyd paint for ten wood species

Wood	Water-based acrylic paint		Oil-based alkyd paint	
	K-value (Unsanded)	K-value (Sanded)	K-value (Unsanded)	K-value (Sanded)
Merbau	0.027	0.022	5.600	4.249
Lamtoro	0.032	0.028	7.452	6.898
Pulai	0.033	0.029	4.506	3.627
Kempas	0.036	0.034	5.148	4.619
Mindi	0.037	0.034	7.447	6.310
Acacia	0.038	0.033	7.260	5.389
FG-Teak	0.038	0.032	5.730	5.038
Durian	0.041	0.035	6.637	6.531
Sungkai	0.052	0.038	5.557	3.485
Afrika	0.055	0.051	9.253	8.202

Note: FG-Teak = Fast growing teak

Sonmez *et al.* (2009) noted that solvent-based alkyd varnish completes its polymerization reaction on the wood surfaces, which allows for chemical bonding on wood surfaces. The lower bonding quality of water-based acrylic varnish is considered because the water used as a solvent causes the swelling of wood fibres and decreases penetration near the wood surfaces, which leads to a weakening of the interface of wood and coating material (Meijer *et al.*, 2000).

4. Conclusion

Based on the results in this work, the following general conclusions were drawn. Sanding with 120 grit number decreased the roughness of the wood surfaces. The equilibrium contact angles increased as the roughness of the planed surface of the woods decreased. The SFE values decreased as the equilibrium contact angles of the wood increased. The higher SFE values generated higher K-values. The higher K-value indicated higher wettability and bonding quality of varnishes. Afrika wood had the greatest SFE and K values among other wood species and produced the highest bonding quality. The solvent-based alkyd varnish was more wettable and generated better bonding quality compared to water-based acrylic varnish. In this work, the K-values of all woods tested were >0, which provides an indication that the varnish liquids (acrylic and alkyd) can spread and penetrate the surface of the woods tested. Improving the quality of especially fast-growing wood from plantation by painting could be considered to spread their use for higher value wood products.

References

- Amorim, M.R.S., Ribeiro, P.G., Martins, S.A., Menezzi, C.H. S.D. and Souza, M.R. (2013), "Surface wettability and roughness of 11 Amazonian tropical hardwoods", *Floresta e Ambiente*, Vol. 20 No. 1, pp. 99-109.
- ASTM (1997), "ASTM D 3359-97: Standard Test Methods for Measuring Adhesion by Tape Test", American Society for Testing and Materials, Philadelphia.
- Baldan, A. (2012), "Adhesion phenomena in bonded joints", *International Journal of Adhesion and Adhesives*, Vol. 38, pp. 95-116.
- Buyuksari, U., Akbulut, T., Guler, C. and Ass, N. (2011), "Wettability and surface roughness of natural and plantation grown narrow leaved ash (*Fraxinus angustifolia* Vahl) wood", *BioResources*, Vol. 6, pp. 4621-4730.
- Crump, D. (1993), *The Complete Guide to Wood Finishes*, Simon and Shuster.
- Darmawan, W., Nandika, D., Massijaya, Y., Kabe, A., Rahayu, I.S., Denaud, L. and Ozarska, B. (2015), "Lathe check characteristics of fast growing Sengon Veneers and their effect on LVL Glue-bond and bending strength", *Journal of Materials Processing Technology*, Vol. 215, pp. 181-188, doi: [10.1016/j.jmatprotec.2014.08.015](https://doi.org/10.1016/j.jmatprotec.2014.08.015).
- Darmawan, W., Nandika, D., Noviyanti, E., Alipraja, I., Lumongga, D., Gardner, D.J. and Gerardin, P. (2018), "Wettability and bonding quality of exterior coatings on Jabon and Sengon wood surfaces", *Journal of Coatings Technology and Research*, Vol. 15 No. 1, pp. 95-104.
- Darmawan, W., Rahayu, I.S., Tanaka, C. and Marchal, R. (2006), "Chemical and mechanical wearing of high-speed steel and tungsten carbide tools by tropical woods", *Journal of Tropical Forest Science*, Vol. 8, pp. 166-172.
- Gavrilovic-Gmusa, I., Dunky, M., Miljkovic, J. and Djiporovic, M. (2012), "Influence of the viscosity of UF resins on the radial and tangential penetration into poplar wood and the shear strength of adhesive joints", *Holzforschung*, Vol. 66 No. 7, pp. 849-856.
- Gindl, M., Reiterer, A., Sinn, G. and Stanzl-Tschegg, S.E. (2004), "Effects of surface ageing on wettability, surface chemistry, and adhesion of wood", *Holz Als Roh- Und Werkstoff*, Vol. 62 No. 4, pp. 273-280.
- Gindl, M., Sinn, G., Reiterer, A. and Tschegg, S. (2001), "Wood surface energy and time dependence of wettability: a comparison of different wood surfaces using an acid-base approach", *Holzforschung*, Vol. 55 No. 4, pp. 433-440.
- International Standard (1997), "Geometrical Product Specifications (GPS) Surface texture: profile method, terms, definitions and surface texture parameters", ISO 4287-1977, International Organization for Standardization, Geneva.
- Kilic, M., Hizioglu, S. and Burdurlu, E. (2005), "Effect of machining on surface roughness of wood", *Building and Environment*, Vol. 41 No. 8, pp. 1072-1078.
- Martawijaya, A., Kartasujana, I., Kadir, K. and Prawira, S. (2005), *Atlas Kayu Indonesia*, Forest Products Research Institute, Bogor.
- Meijer, M., Haemers, S., Cobben, W. and Miltz, H. (2000), "Surface energy determinations of wood: comparison of methods and wood species", *Langmuir*, Vol. 16 No. 24, pp. 9352-9359.
- Moita, A.S. and Moreira, A.L.N. (2003), "Influence of surface properties on the dynamic behaviour of impacting droplets", *9th International Conference on Liquid Atomization and Spray Systems*, Sorrento.
- Piao, C., Winandy, J.E. and Shupe, T.F. (2010), "From hydrophilicity to hydrophobicity: a critical review: part I wettability and surface behaviour", *Wood and Fibre Science*, Vol. 42, pp. 490-510.
- Qin, Z., Chen, H., Gao, Q. and Zhang, S. (2014), "Wettability of sanded and aged fast-growing poplar wood surfaces: I surface free energy", *BioResources*, Vol. 10 No. 1, pp. 1008-1023.
- Rabel, W. (1971), "Einige aspekte der benetzungstheorie und ihre anwendung auf die untersuchung und veränderung der oberflächeneigenschaften von polymeren", *Fabre Und Lack*, Vol. 77, pp. 997-1006.
- Rathke, J. and Sinn, G. (2013), "Evaluating the wettability of MUF resins and pMDI on two different OSB raw materials", *European Journal of Wood and Wood Products*, Vol. 71 No. 3, pp. 335-342.
- SAS Institute (2004), *SAS STAT 9.1 User's Guide*, 1st ed., SAS Institute, Cary, NC.
- Shi, S.Q. and Gardner, D.J. (2001), "Dynamic adhesive wettability of wood", *Wood and Fibre Sci*, Vol. 33, pp. 58-68.
- Sonmez, A., Budakci, M. and Bayram, M. (2009), "Effect of wood moisture content on adhesion of varnish coatings", *Sci. Res. Essay*, Vol. 4, pp. 1432-1437.

Surface roughness

Wayan Darmawan et al.

- Syahirah, A., Paridah, M.T., Hamdan, H., Anwar, U.M.K., Nordahlia, A.S. and Lee, S.H. (2019), "Effect of anatomical characteristics and wood density on surface roughness and their relation to surface wettability of hardwood", *Journal of Tropical Forest Science*, Vol. 31 No. 3, pp. 269-277.
- Wälinder, M. (2002), "Study of Lewis acid-base properties of wood by contact angle analysis", *Holzforschung*, Vol. 56 No. 4, pp. 363-371.
- Wälinder, M.E.P. and Gardner, D.J. (2002), "Acid-base characterization of wood and selected thermoplastics", *Journal of Adhesion Science and Technology*, Vol. 16 No. 12, pp. 1625-1649.

Pigment & Resin Technology

- XLSTAT Addinsoft (2007), A Complete Statistical Add-In for Microsoft Excel, Addinsoft, New York, NY.
- Yuan, Y. and Lee, T.R. (2013), "Contact angle and wetting properties", *Surface Science Techniques*, Vol. 51, pp. 3-34, doi: [10.1007/978-3-642-34243-1](https://doi.org/10.1007/978-3-642-34243-1).
- Yuningsih, I., Rahayu, I.S., Dumasari, L. and Darmawan, W. (2019), "Wettability and adherence of acrylic varnish on long and short rotation teaks", *Journal of Wood Material Science and Engineering*, pp. 1-8., doi: [10.1080/17480272.2019.1575903](https://doi.org/10.1080/17480272.2019.1575903).

Corresponding author

Wayan Darmawan can be contacted at: wayandar@indo.net.id

For instructions on how to order reprints of this article, please visit our website:

www.emeraldgroupublishing.com/licensing/reprints.htm

Or contact us for further details: permissions@emeraldinsight.com

35 hasil tes turnitin pigment influence

ORIGINALITY REPORT

15%

SIMILARITY INDEX

8%

INTERNET SOURCES

11%

PUBLICATIONS

5%

STUDENT PAPERS

PRIMARY SOURCES

1	revistas.ubiobio.cl Internet Source	1%
2	Nadir Ayrilmis, Jan T. Benthien, Heiko Thoemen. "Effects of formulation variables on surface properties of wood plastic composites", Composites Part B: Engineering, 2012 Publication	1%
3	Kilic, M.. "Effect of machining on surface roughness of wood", Building and Environment, 200608 Publication	1%
4	www.repair-home.com Internet Source	1%
5	greedygoblin.blogspot.hu Internet Source	1%
6	Submitted to Universiti Putra Malaysia Student Paper	1%
7	sinta3.ristekdikti.go.id Internet Source	1%

8	Li Zhang, Yingcheng Hu. "Novel lignocellulosic hybrid particleboard composites made from rice straws and coir fibers", Materials & Design, 2014 Publication	1%
9	Wayan Darmawan, Muhammad Azhari, Istie S. Rahayu, Dodi Nandika, Lumongga Dumasari, Indra Malela, Satoru Nishio. "The chips generated during up-milling and down-milling of pine wood by helical router bits", Journal of the Indian Academy of Wood Science, 2018 Publication	1%
10	www.coursehero.com Internet Source	<1%
11	unhas.ac.id Internet Source	<1%
12	es.scribd.com Internet Source	<1%
13	repository.uin-malang.ac.id Internet Source	<1%
14	Submitted to Bartlesville Independent School District #30 Student Paper	<1%
15	Zhong, Z.W., Salim Hizioglu, and C.T.M. Chan. "Measurement of the surface roughness of	<1%

wood based materials used in furniture
manufacture", Measurement, 2013.

Publication

16

pdfs.semanticscholar.org

Internet Source

<1%

17

Kong, L. B., C. F. Cheung, and S. To. "Design, fabrication and characterization of three-dimensional patterned microstructured surfaces with self-cleaning properties from hydrophilic materials", Proceedings of the Institution of Mechanical Engineers Part B Journal of Engineering Manufacture, 2012.

Publication

<1%

18

Mahmoud Darwish, Mohammad Zakaria Nassani. "Evaluation of the effect of denture adhesives on surface roughness of two chemically different denture base resins", European Journal of Dentistry, 2019

Publication

<1%

19

Wayan Darmawan, Dodi Nandika, Yusram Massijaya, Abigael Kabe, Istie Rahayu, Louis Denaud, Barbara Ozarska. "Lathe check characteristics of fast growing sengon veneers and their effect on LVL glue-bond and bending strength", Journal of Materials Processing Technology, 2015

Publication

<1%

20 Bismarck, A.. "Basic surface oxides on carbon fibers", Carbon, 1999 <1 %
Publication

21 Submitted to University of the Phillipines <1 %
Student Paper

22 Songklod Jarusombuti, Nadir Ayrilmis. <1 %
"Oberflächen- und Beschichtungseigenschaften von im Flachpressverfahren hergestellten Holz-Polymer-Werkstoffen", European Journal of Wood and Wood Products, 2010
Publication

23 info.frim.gov.my <1 %
Internet Source

24 Lina Karlinasari, Andi Tri Lestari, Trisna Priadi. " <1 %
Evaluation of surface roughness and wettability of heat-treated, fast-growing tropical wood species sengon ((L.) I.C.Nielsen), jabon ((Roxb.) Miq), and acacia (Willd.) ", International Wood Products Journal, 2018
Publication

25 constellation.uqac.ca <1 %
Internet Source

26 www.mdpi.com <1 %
Internet Source

27 "Biomedical Applications Polymer Blends", <1 %

28

G. Vázquez, J. González-Álvarez, M. S. Freire, J. Santos, R. Uceira, G. Antorrena. "Surface characterization of rotary-peeled eucalyptus veneers by confocal laser scanning microscopy and surface free energy and contact angle determination", WITPRESS LTD., 2009

Publication

29

Kidung Tirtayasa Putra Pangestu, Wayan Darmawan, Dodi Nandika, Hiroshi Usuki. "Cutting performance of multilayer coated tungsten carbide in milling of wood composites", International Wood Products Journal, 2019

Publication

30

tel.archives-ouvertes.fr

Internet Source

31

Submitted to Universiti Sains Malaysia

Student Paper

32

Pigment & Resin Technology, Volume 44, Issue 4 (2015)

Publication

33

Pigment & Resin Technology, Volume 34, Issue 2 (2006-09-19)

Publication

<1%

<1%

<1%

<1%

<1%

<1%

34

edoc.unibas.ch

Internet Source

<1%

35

Wei-Sheng Lei, Kash Mittal, Zhishui Yu.
"Adhesion Measurement of Coatings on
Biodevices/Implants", Wiley, 2017

Publication

<1%

36

Xiaoqian Wang, Fang Wang, Zhiming Yu, Yang
Zhang, Chusheng Qi, Lanxing Du. "Surface free
energy and dynamic wettability of wood
simultaneously treated with acidic dye and flame
retardant", Journal of Wood Science, 2017

Publication

<1%

37

jwoodscience.springeropen.com

Internet Source

<1%

38

journals.sagepub.com

Internet Source

<1%

39

I.M. Mousaa. "Synthesis and performance of
bio-based unsaturated oligomer and containing
gum arabic as a novel protective steel coating
under UV irradiation", Progress in Organic
Coatings, 2020

Publication

<1%

40

Damien Lavigne, Luc Guerrier, Virginie
Gueguen, Jean-Baptiste Michel, Egisto
Boschetti, Olivier Meilhac, Didier Letourneur.
"Culture of human cells and synthesis of

<1%

extracellular matrix on materials compatible with direct analysis by mass spectrometry", *The Analyst*, 2010

Publication

41

Jinzhen Cao, Pascal D. Kamdem. "Surface energy of preservative-treated southern yellow pine (*Pinus* spp.) by contact angle measurement", *Frontiers of Forestry in China*, 2007

Publication

<1%

42

diva-portal.org

Internet Source

<1%

43

Submitted to University of Technology

Student Paper

<1%

44

Submitted to Liverpool John Moores University

Student Paper

<1%

45

Submitted to Varsity College

Student Paper

<1%

46

Submitted to Brunel University

Student Paper

<1%

47

Submitted to City University of Hong Kong

Student Paper

<1%

48

Maziar Sedighi Moghaddam, Per M. Claesson, Magnus E. P. Wålinder, Agne Swerin. "Wettability and liquid sorption of wood

<1%

investigated by Wilhelmy plate method", Wood
Science and Technology, 2013

Publication

49

Mustafa Öncel, Hasan Vurdu, Alperen
Kaymakçı, Osman Emre Özkan, Hakan
Aydoğan. "COATING PERFORMANCES OF
CRIMEAN JUNIPER (*Juniperus excelsa* M.
BIEB.) WOOD", CERNE, 2019

<1%

Publication

Exclude quotes Off

Exclude matches Off

Exclude bibliography On